

# Experimental report

14/02/2018

**Proposal:** 5-41-913

**Council:** 10/2016

**Title:** Detailed crystal structure of SrEr<sub>2</sub>O<sub>4</sub>

**Research area:** Physics

**This proposal is a new proposal**

**Main proposer:** Oleg PETRENKO

**Experimental team:** Simon RIBEROLLES

**Local contacts:** Navid QURESHI

**Samples:** SrEr<sub>2</sub>O<sub>4</sub>

Instrument	Requested days	Allocated days	From	To
D9	3	3	14/02/2017	17/02/2017

## Abstract:

SrEr<sub>2</sub>O<sub>4</sub> is a member of the SrLn<sub>2</sub>O<sub>4</sub> crystalline family known for its high degree of magnetic frustration. SrEr<sub>2</sub>O<sub>4</sub> is a rather interesting member of this family and has already been extensively studied. In fact this compound is known to undergo a magnetic transition at 0.75 K, going from a paramagnetic state to a k=0 ordered state (magnetic structure known). We are now interested to study the in-field magnetic behaviour of SrEr<sub>2</sub>O<sub>4</sub> and recently had the chance to perform an in-field single crystal neutron experiment on WISH at ISIS. We have obtained interesting results from this experiment. To complement this study we are interested to accurately solve the nuclear structure of SrEr<sub>2</sub>O<sub>4</sub> as well as to determine the extinction and absorption coefficients of our single crystal sample. This last task being rather difficult to perform with our WISH data set, this instrument being TOF instrument. It would be ideal to use the D9 instrument for this experiment due to its high Q resolution and the short wave lengths available.

**Experimental report: D9** (Exp. No.5-41-913) Detailed crystal structure of SrEr<sub>2</sub>O<sub>4</sub>.

The measurement was performed on a small high quality single crystal of SrEr<sub>2</sub>O<sub>4</sub> of dimension equal to 1.09, 3.73 and 2.89 mm along *a*, *b* and *c* respectively. The sample was glued on an aluminum pin with *c* aligned parallel to the pin axis. The measurement was performed on D9 in 4-cycle mode. The temperature was set to 20 K and the neutron beam to 0.8 Å. A set of 544 independent reflections was measured considering a large reciprocal space coverage. The dataset was then corrected for absorption with the software Datap. The refinement of the data was then performed with the FullProf suite software giving a good agreement between the structural model obtained and the data (R Bragg = 3.57). In addition to the precise determination of the nuclear structure of SrEr<sub>2</sub>O<sub>4</sub>, the extinctions parameters of the single crystal sample were determined to a high precision. The second part of the experiment was dedicated to a measure of the fully polarised magnetic phase of SrEr<sub>2</sub>O<sub>4</sub> using a cryomagnet. The measurement was performed at 1.5 K under a magnetic field of 2T applied along the Er chains (*b*), the wave length was set at 0.5 Å. In order to isolate the magnetic signal a 1.5 K background measured with no field applied is subtracted from the data. The scale factor is calculated from this data set collected in zero field.

From the irreducible representation performed with Basireps, we have obtained 8 IRs.


Allows for :	$\Gamma_1$	$\Gamma_2$	$\Gamma_3$	$\Gamma_4$	$\Gamma_5$	$\Gamma_6$	$\Gamma_7$	$\Gamma_8$
Antiferromagnetic component within ac-plane	Yes			Yes	yes			yes
Allows for ferromagnetism along b						yes		
Allows for antiferromagnetism along b		yes	yes				yes	
Chi square		39.67	38.50			14	39.7	
Chi <sup>2</sup> combination with $\Gamma_6$	unstable			14.02	unstable			unstable

With a 20.0 kOe magnetic field applied along *b* we are expecting a significant ferromagnetically ordered component of the magnetic structure along this direction. Only  $\Gamma_6$  allows for this specificity and returns the best refinement. The model gives 5.56  $\mu_B$  and 2.0  $\mu_B$  on site one and two respectively (3.78  $\mu_B$  per Er<sup>3+</sup> ions on average), see fig.1.

RF2 -factor : 26.1; RF2w-factor : 25.3; RF -factor : 22.8; Chi2(Intens): 14.0

We have then tried to improve the refinement by combining  $\Gamma_6$  with models allowing for antiferromagnetic component within the ac-plane. This gives us the possibility to combine  $\Gamma_6$  with  $\Gamma_1$ ,  $\Gamma_4$ ,  $\Gamma_5$  and  $\Gamma_8$ . However, none of these combinations returns an improvement to the fits obtained with  $\Gamma_6$  only (the fit does not go directly toward a stable state and keep oscillating between several configurations). In addition, the values obtained from those models for the *x* and *z* components of the magnetic moments are close to 0  $\mu_B$  and are within the range of the calculation uncertainties.

**Conclusion:** From the refinements performed on the data, it is clear that Gamma 6 is the dominant configuration for the magnetic structure. This model is consistent with the fact that we have applied a magnetic field along the b direction and forced the establishment of ferromagnetic order on both sites. Then from our refinements, we have established that allowing for a small antiferromagnetic component within the ac-plane was not improving the fits. The result of this analysis is consistent with the magnetisation measurement performed at 1.5 K and published in (PHYSICAL REVIEW B **78**, 184410\_2008). Interestingly the different site anisotropy is conserved even in the paramagnetic phase, as an application of a magnetic field leads to different sublattice magnetizations. This perfectly agrees with the short-range order and diffuse scattering above TN.

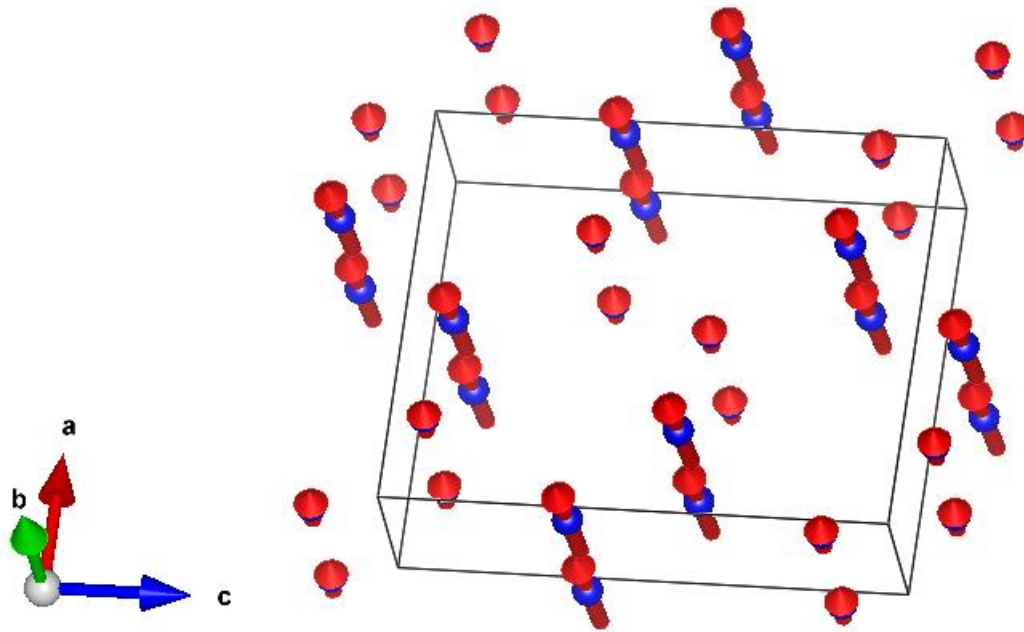

*Figure 1: Field induced magnetic structure of SrEr<sub>2</sub>O<sub>4</sub> stabilised at 1.5 K under magnetic field of 20.0 kOe.*